

## **BLANK PAGE**



# Bolts, Nuts and Fasteners Accessories Sectional Committee, EDC 27 [ Ref : Doc : EDC 27 (1813) ]


### Indian Standard

# SPECIFICATION FOR HEXAGON BOLTS FOR STEEL STRUCTURES

- 1. Scope Requirements for hexagon bolts in the size range 12 to 39 mm for steel structures.
- 2. Dimensions and Tolerances The dimensions of bolts shall be as given in Table 1 and preferred length, diameter combination and clamping lengths for bolts as given in Table 2. The tolerances shall be as given in Fig. 1.

## TABLE 1 DIMENSIONS FOR HEXAGON BOLTS FOR STEEL STRUCTURES

All dimensions in millimetres.

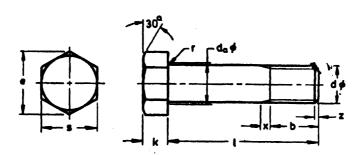

x according to IS: 1369-1961 'Dimensions for screw threads run-outs and undercuts'.

z according to IS: 1368-1967 'Dimensions for ends of bolts and screws (first revision)'.

Siz	•	M12	M16	M20	( M22 )	M24	(M27)	M30	( M33 )	-M36	( M39 )
ď	Nom Max Min	12 13·10 11·57	16 17·10 18·57	20 21·30 19·48	22 23·30 21·48	24 25·30 23·48	27 28:30 26:48	30 31·30 29·48	33 34·60 32·38	36 37·60 35·38	39 40·60 38·38
s < 19 h1 > 19 h1	4 Nom 5 Max 6 Min	19 19:00 18:48	24 24·00 23·16	30 30·00 29·16	32 32·00 31·00	36 36·00 35·00	41 41·00 40·00	46 46·00 45·00	50 50·00 49·00	55 55:00 53:80	56·80 60·00
•	Min	20:88	26·17	32.95	85.03	39.55	45.50	50.85	55:37.	60.79	66:44
A jo16	Nom Max Min	8 8·45 7·55	10 10·45 9·55	13 13·55 12·45	14 14·55 13·45	15 15·58 14·45	17 17·55 16·45	19 19·65 18·35	21 21·65 20·35	23 23·65 22·35	25 25·65 24·35
,	Max	1	1	1	1	1	1	1	1	1	1
de	Max	15.5	19:2	24.4	26.4	28·4	32.4	35·4	38:4	42.4	45.5
b		20	23	26	28	30	33	35	38	40	43

Note - Sizes shown in brackets are of second preference.

Adopted 4 September 1972


© February 1973, BIS

Gr 2

TABLE 2 PREFERRED LENGTH-DIAMETER COMBINATIONS AND CLAMPING LENGTHS
FOR HEXAGON BOLTS FOR STEEL STRUCTURES

(Clause 2)

All dimensions in millimetres.

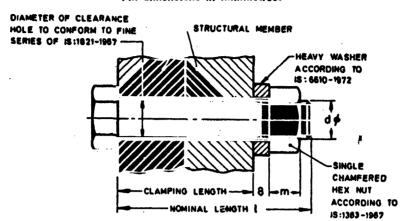

Size	M12	M16	M20	( M22 )	M24	( M27 )	M30	(M33)	M36	( M39 )			
m	10	13	16	18	19	22	24	26	29	31			
Nominal Length /	Clamping Length												
80	5-9												
35	10-14	6-10	0.40										
40	15-19	11-15	8-12	6-10									
45	20-24	16-20	18-17	11-15	9-13								
50	25-29	21-25	18-22	16-20	14-18	1							
55	30-34	26-30	23-27	21-25	19-23								
60	35-39	31-35	28-32	26-30	24-28	21-25							
65	40-44	36-40	33-37	31-35	29-33	26-30							
70	45-49	41-45	38-42	36-40	34-38	31-35							
75	50-54	46-50	43-47	41-45	39-43	36-40							
80	55-59	51-55	48-52	46-50	44-48	41-45	39-43						
85	60-64	56-60	53-57	51-55	49-53	46-50	44-48						
90	65-69	61-65	58-62	56-60	54-58	51-55	49-53						
· <b>95</b>	70-74	66-70	63-67	61-65	59-63	56-60	54-58						
100	75-79	71-75	68-72	66-67	64-68	61-65	59-63	57-61	54-58				
105	80-84	76-80	73-77	71-75	69-73	66-70	64-68	62-66	59-63				
110	85-89	81-85	78-82	76-80	74-78	71-75	69-73	67-71	64-68	62-66			
115	90-94	86-90	83-87	81-85	79-83	76-80	74-78	72-76	69-73	67-71			
120	95-99	91- 95	88- 92	86- 90	84-88	81-85	79-83	77-81	74-78	72-76			
125		96-100	93- 97	91- 95	89-93	86-90	84-88	82-86	79-83	77-81			
130	<u>.</u>	101-105	98-102	96-100	94-98	91-95	89-93	87-91	84-88	82-86			
135		106-110	103-107	101-105	99-103	96-100	94- 98	92- 96	89- 93	87- 9			
140		111-115	108-112	106-110	104-108	101-105	99-103	97-101	94- 98	92- 9			
145		116-120	113-117	111-115	109-113	106-110	104-108	102-106	99-103	97-10			
150		121-125	118-122	116-120	114-118	111-115	109-113	107-111	104-108	102-10			
155	1		123-127	121-125	119-123	116-120	114-118	112-116	109-113	107-11			
160			128-132	126-130	124-128	121-125	119-123	117-121	114-118	112-11			
165			: 133-137	131-135	129-133	126-130	124-128	122-126	119-123	117-12			
170	i		138-142	136-140	134-138	131-135	129-133	127-131	124-128	122-12			
175			143-147	141-145	139-143	136-140	184-138	132-136	129-133	127-18			
180				146-150	144-148	141-145	139-143	137-141	134-138	132-13			
185	1			151-155	149-153	146-150	144-148	142-146	139-143	137-14			
190	1			156-160	154-158	151-155	149-153	147-151	144-148	142-14			
195 200	1		!	161-165	159-163	156-160	154-158 159-163	152-156 157-161	149-153 154-158	147-15 152-15			
200	1	1 .	1	100-170	104-100	101-100	198-199	197-191	194.199	102010			

Note -- Nominal lengths against which clamping lengths are indicated, are preferred.

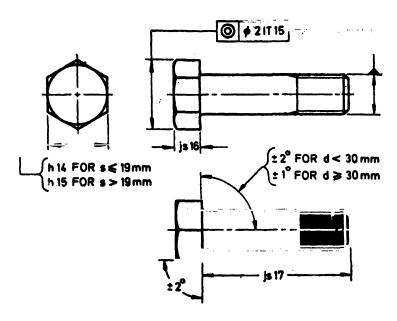


FIG. 1 TOLERANCES FOR HEXAGON BOLTS FOR STEEL STRUCTURES

- 3. Mechanical Properties The mechanical properties of the bolts shall conform to the property class 4.6 or 6.6 as specified in IS: 1367-1967 'Technical supply conditions for threaded fasteners (first revision)'.
- 4. Grade Black (B) grade according to IS: 1367-1967.
- 5. Designation The hexagon bolts shall be designated by the size, length, the number of this standard and the property class.

#### Example:

A hexagon bolt of size M12, length 30 mm conforming to this standard and of property class 4.6 shall be designated as:

Hex Bolt M12 x 30 IS: 6639 4.6

5.1 Where the bolts are required with hexagon nuts (see 6.3), they shall be designated as:

A hexagon bolt of size M12, length 30 mm and property class 4.6 with a hexagon nut shall be designated as:

Hex Bolt M12 x 30N IS: 6639 4.6

### 6. General Requirements

- 6.1 Sampling The method of sampling and acceptance criteria is to be in accordance with 1S: 2614-1969 'Methods for sampling of fasteners ( first revision ) '.
- 6.2 The hexagon bolts shall comply with the requirements of IS: 1367-1967 in respect of requirements not specified in this standard.
- **6.3** The hexagon nuts used with hexagon bolts shall conform to requirements given in IS: 1363-1967 'Black hexagon bolts, nuts and lock nuts (dia 6 to 39 mm) and black hexagon screws (dia 6 to 24 mm) (first revision)' in all respects.
- 6.4 The bolts shall be supplied in natural finish unless otherwise specified by the purchaser. At the request of the purchaser they may be galvanized as per IS: 5358-1969 'Hot-dip galvanized coating on fasteners'.
- 6.5 The approximate weight of hexagon bolts with nuts has been given in Appendix A for the guidence of the purchaser.

## APPENDIX A

( Clause 6.5 )

# APPROXIMATE WEIGHT OF HEXAGON BOLTS WITH NUTS (FOR 1 000 PIECES IN kg)

Size Length / (mm)	M12	M16	M20	(M22)	M24	( M27 )	M30	(1632)	M36	( M39
30	57:5									
35	65.0	117							-	
40	66.4	125	222	281						,•
45	70.8	133	234	296	369					
50°	75.3	141	247	311	387					
55	79.7	149	259	326	405					
60	84.5	157	272	341	423	585				
65	88.6	164	284	356	440	607				
70	93.0	172	296	370	A58	630				
75	97.5	180	309	385	476	652				
80	102	188	321	400	494	675	.699			
85	107	196	334	415	511	697	917			
90	111	204	346	430	529	720	945			
95	116	212	358	445	547	742	972			
100	120	220	871	460	565	765	1 000	1 250	1 560	
105	124	228	363	475	582	787	1 030	1 280	1 600	
110	129	236	395	490	600	810	1 000	1 310	1 640	2 010
115	134	244	407	504	618	832	1 090	1 350	1 680	2 05
120	138	252	420	519	636	855	1 110	1 380	1.720	2 10
125	-	260	432	534	653	877	1 140	1 410	1 760	2 14
130		267	445	540	671	900	1 170	1 450	1 800	2 19
135	<b>i</b>	275	457	564	689	922	1 200	1 480	1 840	2 24
140	·	283	469	579	707	945	1 220	1 510	1 880	2 29
145		291	482	594	724	967	1 250	1 550	1 920	2 33
150	·	299	494	606	742	990	1 280	1 580	1 960	2 38
155	\ <u></u>	<del> </del>	506	623	760	1 010	1 310	1 610	2 000	2 42
160	-		519	638	778	1 030	1 340	1 650	2 040	2 47
165		<del> </del>	531	653	795	1 050	1 360	1 680	2 080	2 51
170		<del> </del>	543	660	813	1 080	1 390	1 710	2 120	2 50
175	-	<b> </b>	556	683	831	1 100	1 420	1 750	2 160	2 610
180	<del> </del>		-	698	849	1 120	1 450	1 780	2 200	2 00
185	<b></b>			718	866	1 140	1 470	1 820	2 240	2710
190				728	884	1 170	1 500	1 860	2 260	2 70
195	<del> </del>	1		743	902	1 190	1 530	1 880	2 320	2 80
200	-	<del> </del>		758	920	1 210	1 500	1:920	2 860	2 85

## EXPLANATORY NOTE

In the preparation of this standard, assistance has been derived from Draft ISO proposal for hexagon bolts [ ISO/TC 2 ( Sectt 290 ) 458 ].

# IS: 6639 - 1972 SPECIFICATION FOR HEXAGON BOLTS FOR STEEL STRUCTURES

# AMENDMENT NO. 1 APRIL 1978 Addendum

(Page 3, clause 3) - Add the following new clause after 3:

'3.1 The bolts shall withstand a minimum shear stress of 260 MPa.


NOTE - The shear stress specified is explicitly intended for bolt testing purposes and is not related to actual design stresses.

## AMENDMENT NO. 2 OCTOBER 1981

#### Alterations

( Page 1, Table 1 ):

a) Figure — Substitute the following for the existing figure:

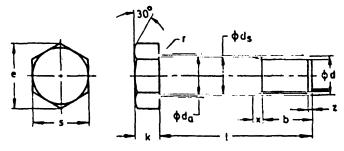

- b) First column, heading Substitute ' Size d' for ' Size'.
- c) Entries for Size 'd' Substitute the following for the existing entries:

			4								
	Nom	12	16	20	22	24	27	30	33	36	39
ds ± 1T15	Max Min	12·70 11·30	16·70 15·30	20·84 19·16	22·84 21·16	_	27·84 26·16	30·34 29·16	34·00 32·00	37·00 35·00	40.00 38.00

( Page 2, Table 2 ):

- a) Legend in Figure Substitute DIAMETER OF CLEARANCE HOLE TO CONFORM TO MEDIUM SERIFS OF IS: 1821-1967 ' for DIAMETER OF CLEARANCE HOLE TO CONFORM TO FINE SERIES OF IS: 1821-1967'.
- b) First column, heading Substitute 'Size d' for 'Size '.

( EDC 27 )

## AMENDMENT NO. 3 DECEMBER 1989

# IS: 6639 - 1972 SPECIFICATION FOR HEXAGON BOLTS FOR STEEL STRUCTURES

( Page 3, clause 3) — Substitute the following for the existing clause:

"3. Mechanical Properties — The mechanical properties of the bolts shall conform to the property class 4.6 or 5.6 as specified in IS 1367 (Part 3): 1979 'Technical supply conditions for threaded steel fasteners: Part 3 Mechanical properties and test methods for bolts, screws and studs with full loadability (second revision)'."

( Page 3, clause 4) — Substitute the following for the existing clause:

"4. Product Grade — Shall be of product grade C according to IS 1367 (Part 2): 1979 'Technical supply conditions for threaded steel fasteners: Part 2 Product grades and tolerances (second revision)'."

( Page 3, clause 6.2) — Substitute the following for the existing clause:

"6.2 In respect of the requirements not covered in this standard the hexagon bolts shall comply with the requirements of IS 1367 (Part 1): 1980 'Technical supply conditions for threaded steel fasteners: Part 1 Introduction and general information (second revision)'."

( Page 3, clause 6.3) — Substitute the following for the existing clause:

"6.3 The hexagon nuts used with the hexagon bolts shall conform to IS 1363 (Part 3): 1984 'Hexagon head bolts, screws and nuts of product grade C: Part 3 Hexagon nuts (size range M 5 to M 36)'."

( Page 3, clause 6.4) — Substitute the following for the existing clause:

"6.4 The bolts shall be supplied in natural finish unless otherwise specified by the purchaser. At the request of purchaser, the bolts may be galvanized as per IS 1367 (Part 13): 1983 'Technical supply conditions for threaded steel fasteners: Part 13 Hot-dip galvanized coatings on threaded fasteners (second revision)"."

(EDC 27)

# AMENDMENT NO. 3 DECEMBER 1989

## IS: 6639 - 1972 SPECIFICATION FOR HEXAGON BOLTS FOR STEEL STRUCTURES

( Page 3, clause 3) — Substitute the following for the existing clause:

"3. Mechanical Properties — The mechanical properties of the bolts shall conform to the property class 4.6 or 5.6 as specified in IS 1367 (Part 3): 1979 'Technical supply conditions for threaded steel fasteners: Part 3 Mechanical properties and test methods for bolts, screws and studs with full loadability (second revision)'."

( Page 3, clause 4) — Substitute the following for the existing clause:

"4. Product Grade — Shall be of product grade C according to IS 1367 (Part 2): 1979 'Technical supply conditions for threaded steel fasteners: Part 2 Product grades and tolerances (second revision)'."

(Page 3, clause 6.2) — Substitute the following for the existing clause:

"6.2 In respect of the requirements not covered in this standard the hexagon bolts shall comply with the requirements of IS 1367 (Part 1): 1980 'Technical supply conditions for threaded steel fasteners: Part 1 Introduction and general information (second revision)'."

( Page 3, clause 6.3) — Substitute the following for the existing clause:

"6.3 The hexagon nuts used with the hexagon bolts shall conform to IS 1363 (Part 3): 1984 'Hexagon head bolts, screws and nuts of product grade C: Part 3 Hexagon nuts (size range M 5 to M 36)'."

( Page 3, clause 6.4) — Substitute the following for the existing clause:

"6.4 The bolts shall be supplied in natural finish unless otherwise specified by the purchaser. At the request of purchaser, the bolts may be galvanized as per IS 1367 (Part 13): 1983 'Technical supply conditions for threaded steel fasteners: Part 13 Hot-dip galvanized coatings on threaded fasteners (second revision)."

(EDC 27)

## AMENDMENT NO. 5 NOVEMBER 1999 TO

# IS 6639: 1972 SPECIFICATION FOR HEXAGON BOLTS FOR STEEL STRUCTURES

(Page 3, clause 3) — Substitute the following for the existing clause:

"3. Mechanical Properties — The mechanical properties of the hexagon bolts shall conform to the property class 4.6 or 5.6 as specified in IS 1367 (Part 3): 1991 'Fasteners — Threaded steel — Technical supply conditions: Part 3 Mechanical properties and test methods for bolts, screws and study with full loadability (third revision)'."

(Page 3, clause 6.1) — Substitute the following for the existing clause:

"6.1 Sampling, Inspection and Acceptance Criteria — The method of sampling, inspection and acceptance criteria shall be in accordance with IS 1367 (Part 17): 1996 'Industrial fasteners — Threaded steel fasteners — Technical supply conditions Part: 17 Inspection, sampling and acceptance procedure'."

(Page 3, clause 6.3) — Substitute the following for the existing clause:

- "6.3 The hexagon nuts used with the hexagon bolts shall conform to IS 1363 (Part 3): 1992 'Hexagon head bolts, screws and nuts of product grade C: Part 3 Hexagon nuts (size range M5 to M64) (third revision)'.
- **6.3.1** The hot-dip galvanized hexagon nuts used with the hot-dip galvanized hexagon bolts shall conform to IS 14394: 1996 'Industrial fasteners Hexagon nuts of product grade C Hot-dip galvanized Specification (size range M12 to M36)'."

(LM 14)

# AMENDMENT NO. 4 NOVEMBER 1990 TO IS 6639:1972 SPECIFICATION FOR HEXAGON BOLTS FOR STEEL STRUCTURES

[Page 3, clause 3 (see also Amendment No. 3)] - Insert the following after 3:

'3.1 For tensile, proof load and wedge loading tests, three threads (3 X P) only shall be exposed between the grips. This is obtained by freely running the nut or fixture to the fullest extent and then unscrewing the specimen three full turns.'

(LMD 14)

Reprography Unit, BIS, New Delhi, India