

इंटरनेट

मानक

### Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

“जानने का अधिकार, जीने का अधिकार”

Mazdoor Kisan Shakti Sangathan

“The Right to Information, The Right to Live”

“पुराने को छोड़ नये के तरफ”

Jawaharlal Nehru

“Step Out From the Old to the New”

IS 12830 (1989): Rubber based adhesives for fixing PVC tiles to cement [PCD 12: Plastics]



“ज्ञान से एक नये भारत का निर्माण”

Satyanarayan Gangaram Pitroda

“Invent a New India Using Knowledge”



“ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है”

Bhartrhari—Nitiśatakam

“Knowledge is such a treasure which cannot be stolen”



BLANK PAGE



*Indian Standard*

**RUBBER BASED ADHESIVES FOR  
FIXING PVC TILES TO CEMENT —  
SPECIFICATION**

**भारतीय मानक**

**सीमेंट पर पी वी सी टाइलें जमाने के लिए रबड़ के आसंजक — विशिष्ट**

UDC 665'939 : 678'061

© BIS 1990

**BUREAU OF INDIAN STANDARDS**  
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG  
NEW DELHI 110002

May 1990

Price Group 2

## FOREWORD

This Indian Standard was adopted by the Bureau of Indian Standards on 6 November 1989, after the draft finalized by the Adhesives Sectional Committee had been approved by the Petroleum, Coal and Related Products Division Council.

These types of adhesives are used for bonding PVC tiles to cement on the floors and walls of buildings.

This standard contains requirements for colour ( **3.1** ), consistency ( **3.2** ) and open assembly time ( **3.4** ) which call for agreement between the purchaser and the supplier.

For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated, expressing the result of a test or analysis, shall be rounded off in accordance with IS 2 : 1960 'Rules for rounding off numerical values (*revised*)'. The number of significant places retained in the rounded off value should be the same as that of the specified value in this standard.

## *Indian Standard*

# RUBBER BASED ADHESIVES FOR FIXING PVC TILES TO CEMENT — SPECIFICATION

### 1 SCOPE

**1.1** This standard prescribes the requirements and methods of sampling and test for rubber based adhesives used for bonding PVC tiles to cement, floors and walls of buildings.

### 2 REFERENCES

**2.1** The following Indian Standards are necessary adjuncts to this standard:

<i>IS No.</i>	<i>Title</i>
---------------	--------------

IS 715 ( Part 2 ) : 1976	Specification for coated abrasive: Part 2 Special and mechanized application ( <i>third revision</i> )
-----------------------------	--

### 3 REQUIREMENTS

#### 3.1 Description

The material shall be manufactured from rubber, compounding ingredients, resins and appropriate solvents. The colour of the material shall be compatible with the application of the material as may be agreed to between the purchaser and the supplier.

#### 3.2 Consistency

The material shall be of a consistency suitable for its mode of application.

#### 3.3 Open Assembly Time

The open assembly time shall be as agreed to between the purchaser and the supplier depending upon the application and shall not vary from batch to batch.

#### 3.4 Adhesion Strength

The adhesion strength shall be as follows.

##### 3.4.1 Strength of Joint in Shear

When tested as prescribed in Annex A, the material shall have shear strength not less than

8 kg/cm<sup>2</sup> after conditioning in standard atmospheric condition (A-4) and not less than 6 kg/cm<sup>2</sup> after heat ageing (Annex B) and immersion in water (Annex C).

#### 3.5 Keeping Quality

The material shall comply with the requirements specified in 3.1 to 3.4 when it has been stored in the original closed containers according to the manufacturer's instructions for a minimum period of one year from the date of manufacture.

### 4 PACKING AND MARKING

#### 4.1 Packing

The material shall be securely packed in airtight containers as agreed to between the purchaser and the supplier.

#### 4.2 Marking

The packages shall be marked legibly and indelibly with the following information:

- a) Name of the material;
- b) Indication of the source of manufacture;
- c) Date by which the material becomes unusable;
- d) Mass or volume of the material in the package;
- e) Direction for storage, if any;
- f) Batch number or month and year of manufacture; and
- g) Time taken, if any, for attaining the full bond strength.

**4.2.1** The manufacturer shall also furnish written instructions on the lines as given below:

- a) Preparation of cement surface;
- b) Method of application of adhesive; and
- c) Maximum and minimum open and closed assembly times.

## ANNEX A

### ( Clause 3.4.1 )

#### TEST FOR SHEAR STRENGTH OF JOINT

##### A-1 APPARATUS

###### A-1.1 Tensile Testing Machine

Any suitable motor driven, tensile strength testing machine may be used. The capacity of the machine shall be such that any reading taken during or on completion of the test shall fall within the loading range ( loading range being the range within which the indicated load shown by calibration is correct within 1.5 percent ). The speed of the moving head of the tensometer when running free shall be  $250 \pm 50$  mm per minute.

###### A-1.2 Roller

A steel roller of  $135 \pm 2$  mm diameter and  $90 \pm 1$  mm width covered with rubber approximately 6 mm thick having a hardness of  $80 \pm 1$  RHD shall be used. The weight of the roller, which applies pressure to the specimen shall be 10 kg. It shall be so constructed that the weight of the handle is not added to the weight of the roller during use ( *see* Fig. 1 ).

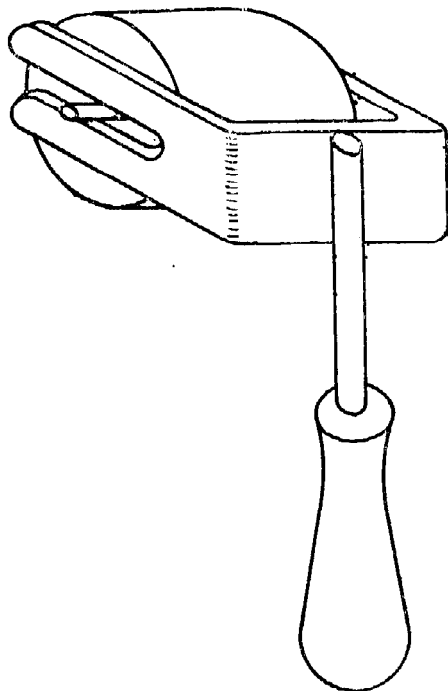


FIG. 1 ROLLER FOR ADHESION STRENGTH TEST

##### A-2 NUMBER OF TEST SPECIMENS

**A-2.1** The test shall be carried out on three test specimens.

##### A-3 PREPARATION OF TEST SPECIMENS

**A-3.1** Take strips of asbestos sheet of 5 mm thickness measuring  $150 \times 25$  mm. Make strips of PVC tiles measuring  $150 \times 25$  mm. Buff the surface of PVC tiles and asbestos sheet with an emery coated abrasive paper No. 50 [ *see* IS 715 ( Part 2 ) : 1976 ] and then dust off with a flat 2.5 cm brush. Over an area measuring  $25 \times 2.5$  mm at one end of surface of asbestos sheet and buffed tile, apply sufficient quantity of adhesive so that a uniform layer of adhesive is formed on both asbestos sheet and tile surfaces. Allow to remain in open air for 10 to 15 minutes. At this time when the adhesive film is dry to a point and there is still an aggressive tackiness but not sticking to the finger when touched, align the coated surfaces of asbestos and tile face to face carefully, without entrapping air, in such a way that the free ends of the strips lie in opposite directions. Press the joint in a suitable press at a pressure of 8 to 10 kg/cm<sup>2</sup>. Allow the bonded specimen to dry under prevailing conditions of temperature and humidity for 24 hours.

##### A-4 CONDITIONING

**A-4.1** Condition the test specimens for 48 hours at a temperature of  $27 \pm 2^\circ\text{C}$  and  $65 \pm 5$  percent relative humidity.

##### A-5 PROCEDURE

**A-5.1** Fix the two free ends of the test specimen in the two jaws of the testing machine which shall be 125 mm apart. Use shims ( *see* Note ) in the grips so that the test specimen is properly centred and is held straight in the grips and the applied force is in the plane of the bonded area. Record the load required to separate or break the joint.

**NOTE** — The shims may be blocks of metal, wood or similar material. The thickness of the shim shall be such that the sum of its thickness and that of the free end of the strip shall be equal to the total thickness at the sandwich area.

##### A-6 REPORT

**A-6.1** Report the shear strength in kg/cm<sup>2</sup>, calculated from the load required to separate or break the joint and the area of the joint, for each test specimen and the mean of the three values.

**ANNEX B**  
**( Clause 3.4.1 )**

**SHEAR STRENGTH AFTER HEAT AGEING**

**B-1** The test specimen prepared as prescribed and then tested for shear strength as prescribed in Annex A shall be kept in an air oven maintained at a temperature of  $70 \pm 2^{\circ}\text{C}$  for 100 h in Annex A.

**ANNEX C**  
**( Clause 3.4.1 )**

**SHEAR STRENGTH AFTER WATER IMMERSION**

**C-1** The test specimen prepared as prescribed in Annex A shall be immersed in water at  $27 \pm 20^{\circ}\text{C}$  for 24 hours and then tested for shear strength as prescribed in Annex A.



### **Standard Mark**

The use of the Standard Mark is governed by the provisions of the *Bureau of Indian Standards Act, 1986* and the Rules and Regulations made thereunder. The Standard Mark on products covered by an Indian Standard conveys the assurance that they have been produced to comply with the requirements of that standard under a well defined system of inspection, testing and quality control which is devised and supervised by BIS and operated by the producer. Standard marked products are also continuously checked by BIS for conformity to that standard as a further safeguard. Details of conditions under which a licence for the use of the Standard Mark may be granted to manufacturers or producers may be obtained from the Bureau of Indian Standards.

## Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 1986* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

### Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Director (Publications), BIS

### Revision of Indian Standards

Indian Standards are reviewed periodically and revised, when necessary and amendments, if any, are issued from time to time. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition. Comments on this Indian Standard may be sent to BIS giving the following reference:

Doc : No. PCDC 15 ( 697 )

#### Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

## BUREAU OF INDIAN STANDARDS

### Headquarters :

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002  
Telephones : 331 01 31, 331 13 75

Telegrams : Manaksanstha  
( Common to all Offices )

### Regional Offices :

	Telephone
Central : Manak Bhavan, 9 Bahadur Shah Zafar Marg, NEW DELHI 110002	{ 331 01 31 331 13 75
Eastern : 1/14 C. I. T. Scheme VII M, V. I. P. Road, Maniktola CALCUTTA 700054	37 86 62
Northern : SCO 445-446, Sector 35-C, CHANDIGARH 160036	2 18 43
Southern : C. I. T. Campus, IV Cross Road, MADRAS 600113	41 29 16
Western : Manakalaya, E9 MIDC, Marol, Andheri ( East ) BOMBAY 400093	6 32 92 95

Branches : AHMADABAD. BANGALORE. BHOPAL. BHUBANESHWAR.  
COIMBATORE. FARIDABAD. GHAZIABAD. GUWAHATI.  
HYDERABAD. JAIPUR. KANPUR. PATNA. TRIVANDRUM.