

इंटरनेट

मानक

Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

“जानने का अधिकार, जीने का अधिकार”

Mazdoor Kisan Shakti Sangathan

“The Right to Information, The Right to Live”

“पुराने को छोड़ नये के तरफ”

Jawaharlal Nehru

“Step Out From the Old to the New”

IS 13360-10-7 (2004): Plastics - Methods of Testing, Part 10: Resin (Thermosetting Properties), Section 7: Phenol-Formaldehyde Mouldings - Determination of Acetone-Soluble Matter (Apparent Resin Content of Material [PCD 12: Plastics])



“ज्ञान से एक नये भारत का निर्माण”

Satyanarayan Gangaram Pitroda

“Invent a New India Using Knowledge”



“ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है”

Bhartrhari—Nitiśatakam

“Knowledge is such a treasure which cannot be stolen”

BLANK PAGE



भारतीय मानक
प्लास्टिक — परीक्षण पद्धतियाँ

भाग 10 रेज़िन (ताप दृढ़ गुणधर्म)

अनुभाग 7 फिनॉल-फार्मएल्डिहाइड संचकन — एसीटोन में घुलनशील पदार्थ ज्ञात करना
(असंचिक स्थिति में सामग्री का दृष्ट रेज़िन अंश)

Indian Standard
PLASTICS — METHODS OF TESTING

PART 10 RESIN (THERMOSETTING PROPERTIES)

Section 7 Phenol-Formaldehyde Mouldings — Determination of Acetone-Soluble
Matter (Apparent Resin Content of Material in the Unmoulded State)

ICS 83.080.10

© BIS 2004

BUREAU OF INDIAN STANDARDS
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI 110002

August 2004

Price Group 2

NATIONAL FOREWORD

This Indian Standard (Part 10/Sec 7) which is identical with ISO 308 : 1994 'Plastics — Phenolic moulding materials — Determination of acetone-soluble matter (apparent resin content of material in the unmoulded state)' issued by the International Organization for Standardization (ISO) was adopted by the Bureau of Indian Standards on the recommendations of the Plastics Sectional Committee and approval of the Petroleum, Coal and Related Products Division Council.

The text of ISO Standard has been proposed to be approved as suitable for publication as an Indian Standard without deviations. Certain conventions are, however, not identical to those used in Indian Standards. Attention is particularly drawn to the following:

- a) Wherever the words 'International Standard' appear referring to this standard, they should be read as 'Indian Standard'.
- b) Comma (,) has been used as a decimal marker while in Indian Standards, the current practice is to use a point (.) as the decimal marker.

CROSS REFERENCES

In this adopted standard reference appears to International Standards listed below for which Indian Standards also exist. The corresponding Indian Standards, which are to be substituted in their place, are given below along with their degree of equivalence for the editions indicated. However, that International Standard cross-referred in this adopted ISO Standard which has subsequently been revised, position in respect of latest ISO Standard has been given:

<i>International Standard</i>	<i>Corresponding Indian Standard</i>	<i>Degree of Equivalence</i>
ISO 472 : 1999 Plastics — Vocabulary	IS 2828 : 2001 Plastics — Vocabulary (first revision)	Identical
ISO 800 : 1992 Plastics — Phenolic moulding materials — Specification	IS 1300 : 1994 Phenolic moulding materials (third revision)	Technically equivalent with minor deviations

For tropical countries like India, the Standard temperature and the relative humidity shall be taken as $27 \pm 2^{\circ}\text{C}$ and 65 ± 5 percent respectively.

In reporting the results of a test or analysis made in accordance with this standard, if the final value, observed or calculated, is to be rounded off, it shall be done in accordance with IS 2 : 1960 'Rules for rounding off numerical values (revised)'.

Indian Standard

PLASTICS — METHODS OF TESTING

PART 10 RESIN (THERMOSETTING PROPERTIES)

Section 7 Phenol-Formaldehyde Mouldings — Determination of Acetone-Soluble Matter (Apparent Resin Content of Material in the Unmoulded State)

1 Scope

This International Standard specifies a gravimetric method for the determination of the amount of matter that can be extracted by acetone, at a temperature near its boiling point, from a sample of finely divided phenolic moulding material. The method applies only to moulding materials based upon novolak resins and not to those based upon resols, as the latter type of resin may not be completely soluble in acetone.

In this International Standard, the amount of acetone-soluble matter is reported as the apparent resin content because, although the extract consists mainly of phenolic resin and hexamine, other acetone-soluble components such as lubricants and colorants or natural resins from the filler are normally also present and will therefore be reported as resin.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 472:1988, *Plastics — Vocabulary*.

ISO 800:1992, *Plastics — Phenolic moulding materials — Specification*.

3 Definitions

For the purposes of this International Standard, the definitions of moulding materials based on phenolic resins, novolak resins and resol resins given in ISO 472 and ISO 800 apply.

4 Principle

The acetone-soluble matter is extracted, using hot acetone, from a finely divided test portion. The extract is dried under controlled conditions and weighed.

5 Reagent

5.1 Acetone, pure.

6 Apparatus

6.1 Reduction device, for reducing coarse materials to a finer state of division.

6.2 Balance, accurate to 1 mg.

6.3 Extraction apparatus, of the type shown in figure 1. (A glass filter crucible may be used instead of a single-thickness extraction thimble.)

The single-thickness extraction thimble, which shall be free from acetone-soluble matter, together with a loose plug of cotton wool, if used, which shall also be free from acetone-soluble matter, shall be dried for 2 h in the oven (6.4) at approximately 105 °C and stored in the desiccator (6.5) until required.

It is permissible to use a modified Soxhlet apparatus, provided that the material in the extraction thimble is surrounded by the vapour of the solvent at its boiling

point. Any other extraction apparatus may be used, provided that it can be shown to give similar results.

6.4 Drying oven, capable of being maintained at approximately 105 °C.

6.5 Desiccator.

6.6 Weighing bottle, with ground-glass stopper.

7 Preparation of sample

7.1 Take a fully representative sample of the moulding material. If the material is in the form of preforms, flakes, coarse pieces or sheet (felted, oriented or woven), reduce it to powder or small pieces using the reduction device (6.1) before the test, taking care to avoid overheating. The thickness of the particles obtained shall not exceed 1,5 mm and their other dimensions shall not exceed 5 mm. The sample

Dimensions in millimetres

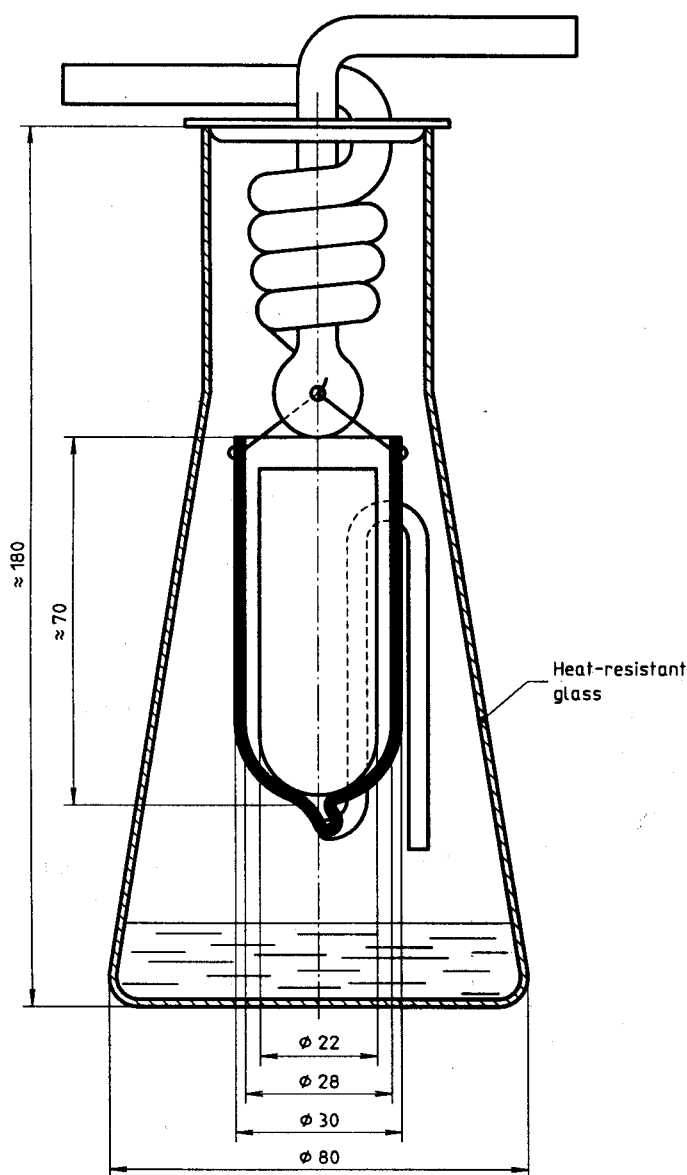


Figure 1 — Extraction apparatus

should not be ground too finely or it may tend to agglomerate in the extraction thimble. Take care that no resin is lost while the sample is being reduced to powder or small pieces.

7.2 Dry at least 6 g of the material at room temperature, *in vacuo* over ρ 1,84 g/ml sulfuric acid or another desiccant, for 24 h.

8 Procedure

8.1 Carry out the test on two test portions of the dried sample (see clause 7).

8.2 Quickly transfer the dried extraction thimble (see 6.3) from the desiccator (6.5) to the weighing bottle (6.6), close the weighing bottle with the stopper and weigh to the nearest 1 mg on the balance (6.2). Remove the stopper from the weighing bottle and place a test portion of approximately 3 g of the dried sample in the extraction thimble. Replace the stopper in the weighing bottle and weigh to the nearest 1 mg.

NOTE 1 If it is desired to know the mass of the empty extraction thimble or to avoid repeating the test in case of breakage, the weighing bottle may be tared or may be weighed separately.

8.3 After folding over the extraction thimble or closing it with a loose plug of absorbent cotton wool, so that none of the material can float out, place it in the siphon tube of the extraction apparatus (6.3). Assemble the condenser, siphon tube and flask to which 100 ml of acetone (5.1) has been added.

8.4 Regulate the heating so that siphoning takes place at a rate of 15 to 30 times per hour, and continue the extraction for $16 \text{ h} \pm 0,5 \text{ h}$. At the end of this time, dry the extraction thimble and contents at room temperature, *in vacuo* over ρ 1,84 g/ml sulfuric acid or another desiccant, for $24 \text{ h} \pm 1 \text{ h}$ and then weigh in the same weighing bottle to the nearest 1 mg.

9 Expression of results

The amount of acetone-soluble matter in the sample (apparent amount of resin in the unmoulded material) expressed as a percentage by mass is given by the formula

$$\frac{m_1 - m_2}{m_1 - m_0} \times 100$$

where

- m_0 is the mass, in grams, of the extraction thimble and weighing bottle;
- m_1 is the mass, in grams, of the extraction thimble weighing bottle and test portion before extraction;
- m_2 is the mass, in grams, of the extraction thimble, weighing bottle and test portion after extraction.

Take the arithmetic mean of the values obtained from the two test portions as the apparent amount of resin in the material under test, provided that these values do not differ by more than 2,0 % (in absolute value).

10 Test report

The test report shall contain the following particulars:

- a) a reference to this International Standard;
- b) all details necessary for complete identification of the sample;
- c) the method used to reduce the material to a finely divided state;
- d) the apparent amount of resin in each test portion;
- e) the arithmetic mean of the values obtained from the two test portions;
- f) the date of the test.

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 1986* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Director (Publications), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the latest issue of 'BIS Catalogue' and 'Standards: Monthly Additions'.

This Indian Standard has been developed from Doc : No. PCD 12 (1798).

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters :

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110 002
Telephones : 2323 0131, 2323 33 75, 2323 9402

Telegrams : Manaksanstha
(Common to all offices)

Regional Offices :

	Telephone
Central : Manak Bhavan, 9 Bahadur Shah Zafar Marg NEW DELHI 110 002	{ 2323 7617 2323 3841
Eastern : 1/14 C.I.T. Scheme VII M, V. I. P. Road, Kankurgachi KOLKATA 700 054	{ 2337 8499, 2337 8561 2337 8626, 2337 9120
Northern : SCO 335-336, Sector 34-A, CHANDIGARH 160 022	{ 60 3843 60 9285
Southern : C.I.T. Campus, IV Cross Road, CHENNAI 600 113	{ 2254 1216, 2254 1442 2254 2519, 2254 2315
Western : Manakalaya, E9 MIDC, Marol, Andheri (East) MUMBAI 400 093	{ 2832 9295, 2832 7858 2832 7891, 2832 7892

Branches : AHMEDABAD. BANGALORE. BHOPAL. BHUBANESHWAR. COIMBATORE. FARIDABAD.
GHAZIABAD. GUWAHATI. HYDERABAD. JAIPUR. KANPUR. LUCKNOW. NAGPUR.
NALAGARH. PATNA. PUNE. RAJKOT. THIRUVANANTHAPURAM. VISAKHAPATNAM.