

इंटरनेट

मानक

Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

“जानने का अधिकार, जीने का अधिकार”

Mazdoor Kisan Shakti Sangathan

“The Right to Information, The Right to Live”

“पुराने को छोड़ नये के तरफ”

Jawaharlal Nehru

“Step Out From the Old to the New”

IS 13360-2-5 (2013): Plastics - Methods of Testing, Part 2: Sampling and Preparation of Test Specimens, Section 5: Multipurpose Test Specimens [PCD 12: Petroleum, Coal, and Related Products]



“ज्ञान से एक नये भारत का निर्माण”

Satyanarayan Gangaram Pitroda

“Invent a New India Using Knowledge”



“ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है”

Bhartrhari—Nitiśatakam

“Knowledge is such a treasure which cannot be stolen”

भारतीय मानक
प्लास्टिक — परीक्षण पद्धतियाँ
भाग 2 परीक्षण नमूनों के नमूने लेना और तैयार करना
अनुभाग 5 बहुउद्देशीय परीक्षण नमूने
(पहला पुनरीक्षण)

Indian Standard
PLASTICS — METHODS OF TESTING
PART 2 SAMPLING AND PREPARATION OF TEST SPECIMENS
Section 5 Multipurpose Test Specimens
(*First Revision*)

ICS 83.080.01

© BIS 2013
BUREAU OF INDIAN STANDARDS
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI 110002

NATIONAL FOREWORD

This Indian Standard (Part 2/Sec 5) (First Revision) which is identical with ISO 3167 : 2002 'Plastics — Multipurpose test specimens' issued by the International Organization for Standardization (ISO) was adopted by the Bureau of Indian Standards on the recommendation of the Plastics Sectional Committee and approval of the Petroleum, Coal and Related Products Division Council.

This standard was originally published in 1997 which was identical with ISO 3167 : 1993. The first revision of this standard has been undertaken to align it with the latest version of ISO 3167 : 2002.

The text of ISO Standard has been approved as suitable for publication as an Indian Standard without deviations. Certain conventions are, however, not identical to those used in Indian Standards. Attention is particularly drawn to the following:

- a) Wherever the words 'International Standard' appear referring to this standard, they should be read as 'Indian Standard'.
- b) Comma (,) has been used as a decimal marker while in Indian Standards, the current practice is to use a point (.) as the decimal marker.

In this adopted standard, reference appears to certain International Standards for which Indian Standards also exist. The corresponding Indian Standards which are to be substituted in their respective place are listed below along with their degree of equivalence for the editions indicated:

<i>International Standard</i>	<i>Corresponding Indian Standard</i>	<i>Degree of Equivalence</i>
ISO 293 : 2004 Plastics — Compression moulding test specimens of thermoplastic materials	IS 13360 (Part 2/Sec 1) ¹⁾ Plastics — Methods of testing: Part 2 Sampling and preparation of test specimens, Section 1 Compression moulding test specimens of thermoplastic materials (<i>first revision</i>)	Identical
ISO 294 -1 : 1996 Plastics — Injection moulding of test specimens of thermoplastic materials — Part 1: General principles, and moulding of multipurpose and bar test specimens	IS 13360 (Part 2/Sec 3) : 2000 Plastics — Methods of testing: Part 2 Sampling and preparation of test specimens, Section 3 Injection moulding of test specimens of thermoplastic materials — General principles and moulding of multipurpose and bar test specimens	Technically Equivalent
ISO 295 : 2004 Plastics — Compression moulding of test specimens of thermosetting materials	IS 13360 (Part 2/Sec 2) : 2013 Plastics — Methods of testing: Part 2 Sampling and preparation of test specimens, Section 2 Compression moulding of test specimens of thermosetting materials (<i>first revision</i>)	Identical
ISO 2818 : 1994 Plastics — Preparation of test specimens by machining	IS 13360 (Part 2/Sec 4) : 1999 Plastics — Methods of testing: Part 2 Sampling and preparation of test specimens, Section 4 Preparation of test specimens by machining (<i>first revision</i>)	do

¹⁾ Under print.

Indian Standard
PLASTICS — METHODS OF TESTING
PART 2 SAMPLING AND PREPARATION OF TEST SPECIMENS
Section 5 Multipurpose Test Specimens
(First Revision)

1 Scope

This International Standard specifies requirements relating to multipurpose test specimens for plastic moulding materials intended for processing by injection or direct compression moulding.

Specimens of types A and B are tensile test specimens from which, with simple machining, specimens for a variety of other tests can be taken (see annex A). Because they have such wide utility, these tensile specimens are referred to in this International Standard as multipurpose test specimens.

The principal advantage of a multipurpose test specimen is that it allows all the test methods mentioned in annex A to be carried out on the basis of comparable mouldings. Consequently, the properties measured are coherent as all are measured with specimens in the same state. In other words, it can be expected that test results for a given set of specimens will not vary appreciably due to unintentionally different moulding conditions. On the other hand, if desired, the influence of moulding conditions and/or different states of the specimens can be assessed without difficulty for all of the properties measured.

For quality-control purposes, the multipurpose test specimen may serve as a convenient source of further specimens not readily available. Furthermore, the fact that only one mould is required may be advantageous.

The use of multipurpose test specimens shall be agreed upon by the interested parties, because there may be significant differences between properties of the multipurpose test specimens and those specified in the relevant test methods.

The main modification with respect to the previous edition of this International Standard lies in narrowing the tolerances on the radius of the shoulder of specimen types A and B. Taking into account the fact that many moulds based on the previous edition are still in use, the changes are introduced as recommendations only. It is intended to change from recommended to mandatory use at the next revision. Thereby a time span of about 10 years is provided, allowing a gradual transition in the course of regular mould replacement. See also annex B.

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this International Standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 293:1986, *Plastics — Compression moulding test specimens of thermoplastic materials*

ISO 294-1:1996, *Plastics — Injection moulding of test specimens of thermoplastic materials — Part 1: General principles, and moulding of multipurpose and bar test specimens*

ISO 295:—¹⁾, *Plastics — Compression moulding of test specimens of thermosetting materials*

ISO 2818:1994, *Plastics — Preparation of test specimens by machining*


1) To be published. (Revision of ISO 295:1991)

ISO 10724-1:1998, *Plastics — Injection moulding of test specimens of thermosetting powder moulding compounds (PMCs) — Part 1: General principles and moulding of multipurpose test specimens*

3 Dimensions of test specimens

For the purposes of this International Standard, the preferred multipurpose test specimen is the type A tensile specimen shown in Figure 1. This can be made suitable for a variety of other tests by simple cutting, because the length l_1 of its narrow parallel-sided portion is $80 \text{ mm} \pm 2 \text{ mm}$.

Dimensions in millimetres

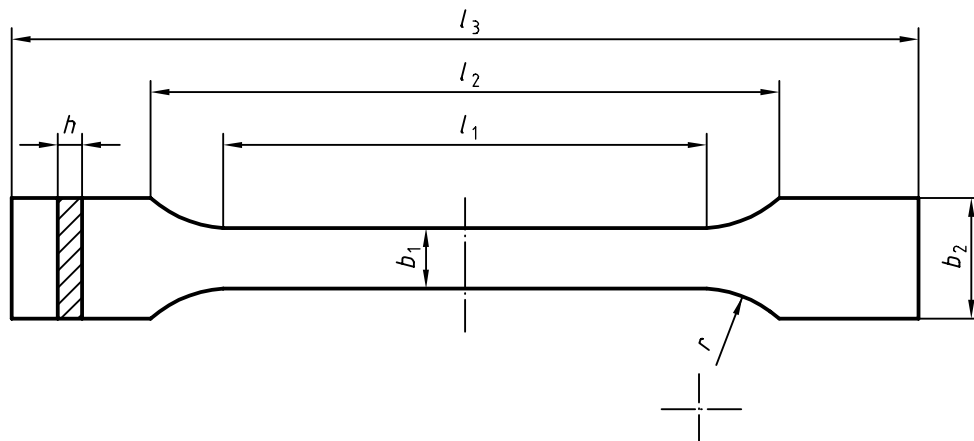

	Specimen type	A	B
l_3	Overall length ^a	≥ 150 Recommended value ^b 170	≥ 150
l_1	Length of narrow parallel-sided portion	80 ± 2	$60,0 \pm 0,5$
r	Radius	20 to 25 Recommended value ^b 24 ± 1	$\geq 60^c$ Recommended value ^b $60,0 \pm 0,5$
l_2	Distance between broad parallel-sided portions ^d	104 to 113	106 to 120 Recommended range ^b 106 to 110
b_2	Width at ends	$20,0 \pm 0,2$	
b_1	Width of narrow portion	$10 \pm 0,2$	
h	Thickness	$4,0 \pm 0,2$	

^a The recommended overall length of 170 mm for type A is consistent with ISO 294-1 and ISO 10724-1. For some materials, the length of the tabs may need to be extended (e.g. to give an overall length of 200 mm) to prevent breakage or slippage in the jaws of the test machine.

^b The recommended values and ranges may become mandatory on occasion of the next revision of the standard. The lower tolerances on the radius reduce the ranges of the stress concentrations that are found at the transitions between the narrow parallel-sided and the rounded portions. Together with the smaller tolerance on the distance between the broad parallel-sided portions for type B, a common value of the initial distance between jaws can be used for tensile testing (see ISO 527-2).

$$^c r = \frac{(l_2 - l_1)^2 + (b_2 - b_1)^2}{4(b_2 - b_1)}$$

^d Resulting from l_1 , r , b_1 and b_2 , but within the indicated tolerance.

Figure 1 — Type A and B multipurpose test specimens

4 Preparation of test specimens

4.1 General

Test specimens shall be prepared in accordance with the relevant material specification. When none exists, specimens shall be either directly compression or injection moulded from the material in accordance with ISO 293, ISO 294-1, ISO 295:— or ISO 10724-1, as appropriate, or machined in accordance with ISO 2818 from plates that have been compression or injection moulded from the compound.

Strict control of all conditions of the specimen preparation is essential to ensure that all test specimens in a set are actually in the same state.

All surfaces of the test specimens shall be free from visible flaws, scratches or other imperfections. With moulded specimens all flash, if present, shall be removed, taking care not to damage the moulded surface.

The broad sides of each specimen shall be suitably marked (see the note), for injection-moulded specimens to distinguish between the sides formed by the cavity plate and the fixed plate of the mould (see ISO 294-1 or ISO 10724-1), for compression-moulded and machined specimens to identify any asymmetry resulting from the underlying moulding process.

NOTE Asymmetry with respect to thickness may influence the flexural properties, including the temperature of deflection under load (see annex A).

For injection-moulded specimens, the sides can be identified by the impressions of the ejection pins and by the draft angle. Compression-moulded and machined specimens shall be marked at their shoulders. ISO bars taken from the central part of multipurpose test specimens shall be marked outside their central 40 mm section, which is loaded by flexural testing.

4.2 Injection moulding of multipurpose test specimens

Type A test specimens shall be injection moulded as specified in ISO 294-1 or ISO 10724-1, as appropriate, and under conditions defined in the relevant International Standard for the material under examination.

4.3 Compression moulding of multipurpose test specimens

Type B test specimens shall be compression moulded directly to their final dimensions as specified in ISO 293 or ISO 295:—, as appropriate, and under conditions defined in the relevant International Standard for the material under examination.

4.4 Machining of multipurpose test specimens

4.4.1 Machining of test specimens shall be performed either as specified in ISO 2818 or as agreed upon by the interested parties.

4.4.2 Test specimens having a width of 10 mm shall be cut symmetrically from the central parallel-sided portion of the multipurpose test specimen.

The surface of the central parallel-sided portion of the test specimen shall remain as moulded:

- The width of the machined portions of the specimen shall be not less than that of the central parallel-sided portion, but may exceed the width of the latter by not more than 0,2 mm.
- During the machining operation, care shall be taken to avoid any damage to the moulded surfaces of the central portion.

For test specimens longer than 80 mm, the broad ends of the type A multipurpose test specimen (or type B for test specimens longer than 60 mm) shall be machined to the width of the central parallel-sided portion.

4.4.3 Type B multipurpose test specimens shall be machined from suitably processed compression-moulded plates (see 4.3).

5 Report on preparation of test specimens

The report shall contain the following information:

- a) a reference to this International Standard;
- b) an indication of the specimen type (A or B);
- c) the type, source, manufacturer's code, grade and form, including history, etc., if known;
- d) the method of moulding and the conditions used;
- e) the method of machining and the conditions used;
- f) the number of test specimens produced;
- g) the standard atmosphere for conditioning, plus any special conditioning treatment if required by the standard for the material or product concerned;
- h) the date of preparation.

Annex A

(informative)

Recommended applications for multipurpose test specimens or parts thereof

Method	Reference ^a	Type of specimen and/or dimensions mm
Tensile test	ISO 527-2	A or B
Tensile creep test	ISO 899-1:—	A or B
Flexural test	ISO 178:2001	80 × 10 × 4
Flexural creep test	ISO 899-2:—	80 × 10 × 4
Compressive test	ISO 604:—	(10 to 50) × 10 × 4
Impact strength — Charpy	ISO 179-1 and ISO 179-2	80 × 10 × 4
Impact strength — Izod	ISO 180	80 × 10 × 4
Impact strength — tensile	ISO 8256	80 × 10 × 4
Temperature of deflection under load	ISO 75-2:—	80 × 10 × 4
Vicat softening temperature	ISO 306	(≥ 10) × 10 × 4
Hardness, ball indentation	ISO 2039-1:2001	(≥ 20) × 20 × 4
Environmental stress cracking	ISO 22088-2:—, ISO 22088-3:— and ISO 22088-4:—	A or B or 80 × 10 × 4
Density	ISO 1183-3	30 × 10 × 4
Oxygen index	ISO 4589-2 and ISO 4589-3	80 × 10 × 4
Comparative tracking index (CTI)	IEC 60112	15 × 15 × 4
Electrolytic corrosion	IEC 60426	30 × 10 × 4
Coefficient of linear expansion	ISO 11359-2	(> 30) × 10 × 4

^a See Bibliography.

Annex B (informative)

Consequences of changes in geometry

B.1 Test specimen length

The length of 170 mm may be too short for some materials in connection with a distance between the grips of 115 mm. While the test specimen length of 170 mm is sufficient for the large majority of tensile tests, clamping problems occasionally arise with highly reinforced grades and with very ductile ones.

If 170 mm is too short for some materials, this is even more true for the length of ≥ 150 mm that was used in the previous edition. The “ \geq ”-sign gives the freedom to use lengths > 170 mm, which is also allowed in this edition. This recommendation is in line with ISO 294-1.

B.2 Radius tolerance

Taking into account the tolerances, the length l_2 between the shoulders is

$$106,125 \text{ mm} \leq l_2 \leq 112,526 \text{ mm} \quad \text{this edition}$$

$$103,996 \text{ mm} \leq l_2 \leq 112,526 \text{ mm} \quad \text{previous edition}$$

The clamping distance (in ISO 527-2) remains unchanged:

$$L = 115 \text{ mm} \pm 1 \text{ mm}$$

The shortest possible distance from clamp to shoulder is:

$$s_{\min} = 0,737 \text{ (same for this and previous edition)}$$

The longest possible distance from clamp to shoulder is:

$$\text{this edition:} \quad 4,932 \text{ mm}$$

$$\text{previous edition:} \quad 6,002 \text{ mm}$$

This is not a very big change, but it affects the effective length. It may be used to determine nominal strain data in the pre-yield range for e.g. modulus determination under severe conditions, where extensometers cannot be used, e.g. in temperature-controlled enclosures, by using grip separation only. However, the effective length is quite sensitive to radius changes, and limiting the radius tolerance reduces possible error sources when utilizing this method. It may be introduced in ISO 527-2 on the occasion of the next revision.

The reduction of the radius tolerance of **machined** specimens allows the use of a common clamping distance of (115 ± 1) mm. This is the main benefit of the proposal.

B.3 Notch factor

When the type A specimen, with a radius of 20 mm to 25 mm, was introduced in addition to the type B specimen (radius ≥ 60 mm) in the previous edition of ISO 3167, calculations were made to compare the two types of specimen.

Assuming linear-elastic material behaviour, notch factors of 1,045 (for $r = 60$ mm) and 1,143 ($r = 20$ mm) were found. Therefore tensile strength differences of about 10 % could be expected, and were also found in machined test specimens of brittle materials. However, when testing injection-moulded specimens, a reduction in tensile strength at yield of

–1 % \pm 1 % (average of 22 materials)

was found. Compared to the radius reduction from 60 mm to 20 mm, the recommended increase from (20 mm to 25 mm) to (23 mm to 25 mm) will result in only a very minor reduction of the notch factor, with negligible effect on the test results.

Changes in tensile strength at yield values due to the radius tolerance reduction for injection-moulded specimens are not to be expected. There may be a slight increase in strain-at-break values.

Bibliography

- [1] ISO 75-2:—¹⁾, *Plastics — Determination of temperature of deflection under load — Part 2: Plastics and ebonite*
- [2] ISO 178:2001, *Plastics — Determination of flexural properties*
- [3] ISO 179-1:2000, *Plastics — Determination of Charpy impact properties — Part 1: Non-instrumented impact test*
- [4] ISO 179-2:1997, *Plastics — Determination of Charpy impact properties — Part 2: Instrumented impact test*
- [5] ISO 180:2000, *Plastics — Determination of Izod impact strength*
- [6] ISO 306:1994, *Plastics — Thermoplastic materials — Determination of Vicat softening temperature (VST)*
- [7] ISO 527-2:1993, *Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion plastics*
- [8] ISO 604:—²⁾, *Plastics — Determination of compressive properties*
- [9] ISO 899-1:—³⁾, *Plastics — Determination of creep behaviour — Part 1: Tensile creep*
- [10] ISO 899-2:—⁴⁾, *Plastics — Determination of creep behaviour — Part 2: Flexural creep by three-point loading*
- [11] ISO 1183-3:1999, *Plastics — Methods for determining the density of non-cellular plastics — Part 3: Gas pyknometer method*
- [12] ISO 2039-1:2001, *Plastics — Determination of hardness — Part 1: Ball indentation method*
- [13] ISO 4589-2:1996, *Plastics — Determination of burning behaviour by oxygen index — Part 2: Ambient-temperature test*
- [14] ISO 4589-3:1996, *Plastics — Determination of burning behaviour by oxygen index — Part 3: Elevated-temperature test*
- [15] ISO 8256:1990, *Plastics — Determination of tensile-impact strength*
- [16] ISO 11359-2:1999, *Plastics — Thermomechanical analysis (TMA) — Part 2: Determination of coefficient of linear thermal expansion and glass transition temperature*
- [17] ISO 22088-2:—⁵⁾, *Plastics — Determination of resistance to environmental stress cracking (ESC) — Part 2: Constant tensile stress method*
- [18] ISO 22088-3:—⁶⁾, *Plastics — Determination of resistance to environmental stress cracking (ESC) — Part 3: Bent strip method*

1) To be published. (Revision of ISO 75-2:1993)

2) To be published. (Revision of ISO 604:1993)

3) To be published. (Revision of ISO 899-1:1993)

4) To be published. (Revision of ISO 899-2:1993)

5) To be published. (Revision of ISO 6252:1992)

6) To be published. (Revision of ISO 4599:1986)

- [19] ISO 22088-4:—⁷⁾, *Plastics — Determination of resistance to environmental stress cracking (ESC) — Part 4: Ball or pin impression method*
- [20] IEC 60112:1979, *Method for determining the comparative and the proof tracking indices of solid insulating materials under moist conditions*
- [21] IEC 60426:1973, *Test methods for determining electrolytic corrosion with insulating materials*

7) To be published. (Revision of ISO 4600:1992)

(Continued from second cover)

<i>International Standard</i>	<i>Corresponding Indian Standard</i>	<i>Degree of Equivalence</i>
ISO 10724-1 : 1998 Plastics — Injection moulding of test specimens of thermosetting powder moulding compounds (PMCs) — Part 1: General principles and moulding of multipurpose test specimens	IS 13360 (Part 2/Sec 10) : 2006 Plastics — Methods of testing: Part 2 Sampling and preparation of test specimens, Section 10 Injection moulding of test specimens of thermosetting powder moulding compounds (PMCs) — General principles and moulding of multipurpose test specimens	Identical

For tropical countries like India, the standard temperature and the relative humidity shall be taken as $27 \pm 2^{\circ}\text{C}$ and 65 ± 5 percent, respectively.

In reporting the result of a test or analysis made in accordance with this standard, if the final value, observed or calculated, is to be rounded off, it shall be done in accordance with IS 2 : 1960 'Rules for rounding off numerical values (*revised*)'.

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act*, 1986 to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Director (Publications), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the latest issue of 'BIS Catalogue' and 'Standards: Monthly Additions'.

This Indian Standard has been developed from Doc No.: PCD 12 (2481).

Amendments Issued Since Publication

Amendment No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

Telephones: 2323 0131, 2323 3375, 2323 9402

Website: www.bis.org.in

Regional Offices:

Telephones

Central	: Manak Bhavan, 9 Bahadur Shah Zafar Marg NEW DELHI 110002	{ 2323 7617 2323 3841
Eastern	: 1/14, C.I.T. Scheme VII M, V.I.P. Road, Kankurgachi KOLKATA 700054	{ 2337 8499, 2337 8561 2337 8626, 2337 9120
Northern	: SCO 335-336, Sector 34-A, CHANDIGARH 160022	{ 260 3843 260 9285
Southern	: C.I.T. Campus, IV Cross Road, CHENNAI 600113	{ 2254 1216, 2254 1442 2254 2519, 2254 2315
Western	: Manakalaya, E9 MIDC, Marol, Andheri (East) MUMBAI 400093	{ 2832 9295, 2832 7858 2832 7891, 2832 7892

Branches: AHMEDABAD. BANGALORE. BHOPAL. BHUBANESHWAR. COIMBATORE. DEHRADUN. FARIDABAD. GHAZIABAD. GUWAHATI. HYDERABAD. JAIPUR. KANPUR. LUCKNOW. NAGPUR. PARWANOO. PATNA. PUNE. RAJKOT. THIRUVANATHAPURAM. VISAKHAPATNAM.